arXiv:cond-mat/0105405v1 [cond-mat.dis-nn] 21 May 2001

From the Dynamically Nanostructured Liquid to the Glassy State: A Phenomenological Approach

J. K. Krüger,[a] J. Petersson,[a] J. Baller[a] and M. Henkel[b]
[a] *Laboratoire Européen de Recherche Universitaire Saarland-Lorraine (LERUSL) and Universität des Saarlandes, Fakultät für Physik* und Elektrotechnik 7.2, Gebäude 38, D-66041 Saarbrücken, Germany*
[b] *LERUSL et Laboratoire de Physique des Matériaux,** Université Henri Poincaré Nancy I, B.P.239, F-54506 Vandœuvre-lès-Nancy Cedex, France*
(February 1, 2008)

Based on experimental evidences we present a phenomenological description of the thermal glass transition as a dynamical phase transition. Different susceptibilities calculated on the basis of this description are in good qualitative agreement with experimental data. As an essential feature this novel view of the glass transition reflects the kinetic as well as the transition aspect of the thermal glass transition.

PACS numbers: 64.70.Pf, 62.20.Dc, 65.60.+a, 78.35.+c

In the last twenty years of theoretical and experimental work on glasses a tremendous amount of details has been elucidated, see [1–5]. The most impressing advances in the understanding of the freezing of liquids were obtained by the mode coupling theory (MCT) [6] and through numerical simulations [7]. Unfortunately, there seems to be no direct bridge [8] from the MCT transition to the thermal glass transition (TGT) because the first one occurs at about 40 K above the TGT. The slow progress in the understanding of the glass problem is probably due to the contradictory experimental findings: The TGT shows clear kinetic as well as phase transition features [9–12]. Because of the obvious kinetic features the majority of the publications in the field (see e.g. [2,13,14]) follows the idea that the TGT is due to an accidental cross-over of time scales, i.e. a cross-over of the structural relaxation times (of the α-relaxation) with the experimental time scales involved. There exist however serious theoretical [15] and experimental [9–12] works which clearly indicate the existence of a well defined glass transition temperature T_{gs}. Our own studies, performed with a novel time domain Brillouin light scattering technique led us to the conclusion that an intrinsic glass transition indeed exists. Moreover the crossing of time scales can be overcome and consequently the intrinsic glass transition at T_{gs} can be detected experimentally [9,10].

Based on experimental facts, we present the following phenomenological description of the TGT as a dynamic phase transition which merges both the influences of the experimentally confirmed transition- and kinetic influences due to the thermal history of the sample on those susceptibilites which are affected by the TGT. We shall test our phenomenological approach with respect to some important experimental facts, which any reliable model calculation should reflect:

i.) The (operative) thermal glass transition temperature, T_g, is displayed by kink-like, jump-like or bending anomalies in static quantities like the mass density, the elastic stiffness constants, the enthalpy, the volume expansion coefficient etc. [2,13]. The static shear stiffness $c_{44}^s(T)$ jumps at the glass transition temperature T_{gs} yielding $c_{44}^s(T) = 0$ for $T > T_{gs}$ and $c_{44}^s(T) = c_{44}^{glass}(T)$ for $T \leq T_{gs}$. ii.) A dynamic glass transition temperature $T_g^{dyn} \geq T_{gs}$ can be defined by the cross-over of the probe frequency ω with the structural relaxation frequency ω_α which accompanies the freezing process. The structural α-relaxation time $\tau_\alpha = \omega_\alpha^{-1}$ is proportional to the shear viscosity of the glass-forming material. At probe frequencies in the GHz regime, the difference $T_g^{dyn} - T_{gs}$ usually exceeds 100 K. The temperature interval $T_{gs} \leq T \leq T_g^{dyn}$ for which $\omega\tau_\alpha \gg 1$ holds is called the slow motion regime. Susceptibilities determined in the slow motion regime are dynamically frozen quantities. In spite of their dynamically clamped character, these susceptibilities like the hypersonic shear stiffness or the refraction index show a kink-like anomaly [16] at the *same* temperature as static quantities like the specific volume [17–19]. The only possibility to relate this kink anomaly to a cross-over of time scales is to find another experimental time-scale independent of the probe frequency. The remaining time usually available in an experiment is due to the cooling scenario. iii.) These kink-like anomalies sharpen with decreasing cooling rates and cannot be shifted continuously to lower temperatures by a further decrease of the cooling rates, there seems to exist a lower boundary for T_g yielding $Min(T_g) = T_{gs}$ [9–12]. iv.) T_g is usually derived from the intersection point of the high temperature with the low temperature asymptote in the case of kink-like and bending anomalies, or by inflection- or onset-points in the case of jump-like anomalies [2,13]. v.) T_g depends on the heating or cooling rate and thus shows kinetic features [2,13]. vi.) Although the absolute values of phenomenological susceptibilities within the glassy state may depend on the thermal history of the sample, *the temperature derivatives of these susceptibilities remain almost invariant* [2,13]. vii.) From the structural point of

view the TGT is an isostructural transition. viii.) Usually the structural glass relaxations (α-process) follow a Vogel-Fulcher-Tamman (VFT) behaviour. *However, on an extremely long time scale, close to the intrinsic glass transition, an Arrhenius law with a cut-off frequency was observed, see fig. 1* [9,10]. ix.) Neither the limiting temperature T_0 due to the VFT behavior nor the Kauzmann temperature T_K of the entropy catastrophe has been observed experimentally [9–12]. x.) The elastic anharmonicity displayed by the longitudinal mode Grüneisen parameter behaves discontinuously at the thermal glass transition and this discontinuity cannot be removed by annealing [20,21].

The basis for the following phenomenological description is the cut-off behaviour of τ_α shown in fig. 1 [9–12]

$$\tau_\alpha(T) = \begin{cases} A\,\mathrm{e}^{\Delta G/RT} & ; \quad T \geq T_{gs} \\ \infty & ; \quad T < T_{gs} \end{cases} \tag{1}$$

with A: inverse attempt frequency, ΔG: activation enthalpy, R: universal gas constant. A similar Arrhenius law with a clear cut-off at a distinguished temperature was found by Lüty et *al.* for the order-disorder transition of CN^- molecules [22]. We assume as a working hypothesis that the TGT is a dynamic phase transition which is governed by the temperature dependent relaxation time given by eq. (1). The model is moreover based on the fact that the TGT shows besides its phase transition character (i, ii, viii, x) obvious kinetic features including non-ergodicity (iii, iv, v, vi, ix). Thus it can hardly be described in the setting of a classical order parameter scenario and critical slowing-down. We assume that within the high-temperature phase the freezing process is accompanied by the formation of nano-sized regions of which we think as of dynamic randomly closed packed clusters (rcp's). Sufficiently close but above T_{gs} the rcp's are dynamically percolated in the sense that they form a temporary chain-network consisting of rcp's which have an average life-time $\tau_\alpha(T)$. $\tau_\alpha(T)$ may be viewed as a temperature-dependent internal clock within the material which defines a unique intrinsic glass transition temperature T_{gs} by the condition that $\omega_\alpha = \tau_\alpha^{-1}(T)$ drives all dynamic properties relevant for the freezing process. Thus we admit that the transition parameter $\omega_\alpha(T)$ controls the glass transition simultaneously in three areas: a) Influence on the structure (see below). b) Dynamic influence: response to a periodic perturbation (probe frequency). c) Kinetic influence: response to temperature perturbation (time domain).

The structural properties close to the the TGT are determined by the mass ratio $x^{rcp} = m^{rcp}/m$ where m is the total mass of the sample and m^{rcp} the total mass of rcp's. If every relevant experimental time constant τ_{exp} is always larger than the instrinsic time constant $\tau_\alpha(T)$, we assume that the concentration of the rcp's is zero at sufficiently high temperatures and has to go continuously to one on approaching T_{gs}. Taking into account that $x^{rcp}(T)$ is intimately related to the specific volume of the glass-forming material, its temperature derivative must jump at T_{gs} although this step in the volume expansion coefficient is often smeared out in experimental data. These basic requirements can be fulfilled by a simple relation depending only on the transition parameter

$$x^{rcp}(T) = \begin{cases} \mathrm{e}^{-(\omega_\alpha(T)-\omega_\alpha(T_{gs}))} & ; \quad T \geq T_{gs} \\ 1 & ; \quad T < T_{gs} \end{cases} \tag{2}$$

Eq. (2) incorporates the idea that at temperatures $T_{gs}+\epsilon$ (where $\epsilon \ll 1$), a stationary interchange between liquid and rcp-phase takes place. As soon as the minimum frequency $\omega_\alpha(T_{gs})$ is reached, any molecular dynamic related to the liquid-glass transition becomes so slow that it spontaneously dies. Although (2) is an *ad hoc* assumption, it works remarkably well in model calculations.

According to our model and in line with experimental data the transition parameter $\omega_\alpha(T)$ furthermore controls dynamic properties like the shear stiffness $c_{44}(T)$ or the shear viscosity $\eta_{44}(T)$. In order to demonstrate the effect of $\omega_\alpha(T)$ on $c_{44}(T)$ in the vicinity of the glass transition we use the Debye-process as the simplest relaxation model. Other relaxation models can easily be incorporated in our phenomenological approach. The real part of the dynamic shear stiffness $c^*_{44}(\omega)$ is given by

$$c^*_{44_{Debye}}(\omega) = \mathrm{i}\omega\eta^*_{44} = \frac{\mathrm{i}\omega\tau_\alpha c^\infty_{44}}{1+\mathrm{i}\omega\tau_\alpha} \tag{3}$$

If the experimental time constant τ_{exp_T} of the cooling or heating process becomes equal or smaller than the structural relaxation time τ_α, the sample will fall out of thermal equilibrium. In other words, in the vicinity of the glass transition the phonon bath controlling the temperature of the sample is already in equilibrium whereas the dynamic "nano-composit" is not. Any quantity $Q(T)$ describing thermal recovery processes close to T_{gs} is expected to depend on $\omega_\alpha(T)$. A simple expression which takes into account the behaviour close to T_{gs} and the dying-out for high T and large τ_{exp_T} is

$$Q(T) = 1 - q_0 \begin{cases} \mathrm{e}^{-\tau_{exp_T}/\tau_\alpha(T)} & ; \quad T \geq T_{gs} \\ \mathrm{e}^{-\tau_{exp_T}/\tau_\alpha(T_{gs})} & ; \quad T < T_{gs} \end{cases} \tag{4}$$

Here q_0 describes the degree of possible quenching. Even in the long-time limit the permanent creation and annihilation of rcp's within the glass-forming liquid permanently changes the network structure and thus hinders the formation of a rigid network above T_{gs}. The appearance of the glass transition will strongly depend on the relative magnitude of each individual influence given by (2), (3) and (4).

Experimentally, the specific volume in the glassy state as well as in the liquid state behaves linear over a wide range of temperatures (e.g. [17–19]) but the volume expansion coefficients of the liquid state are higher than

those of the glassy state ($\alpha_l > \alpha_g$). The position of the operative T_g depends on the cooling rate whereas α_l and α_g remain unchanged [19]. If the mass density is measured with a purely static experimental technique, the only relaxation phenomenon expected is that which emerges from the temperature perturbation on approaching T_{gs}, being expressed by the experimental time scale τ_{exp_T}. We assumed above that sufficiently close but above T_{gs} the rcp's are above the percolation threshold. This condition guarantees the onset of mechanical rigidity of glass-forming samples at T_{gs} (i). When approaching T_{gs} from above, from (2) the rcp concentration increases towards one. At the same time the related network needs increasing time in order to reach its dynamic equilibrium structure. The equilibrium specific volume $v^{eq}(T)$ depends on the specific volume of the liquid part $v^l(T) = v^{l_0}(1 + \alpha^l(T - T_{gs}))$, on the rcp part $v^{rcp}(T) = v^{rcp_0}(1 + \alpha^{rcp}(T - T_{gs}))$, and on $x^{rcp}(T)$

$$v^{eq}(T) = v^l(T)(1 - x^{rcp}(T)) + v^{rcp}(T)x^{rcp}(T) \qquad (5)$$

Thus the ideal glass transition described by $v^{eq}(T)$ is determined by the kink-like anomaly of $x^{rcp}(T)$ at T_{gs}. In order to incorporate the competition between the thermal treatment given by τ_{exp_T} and the transition parameter ω_α on the specific volume given by eq. (5), we use the following simple relation

$$v(T) = Q(T, \tau_{exp_T})v^{eq}(T) \qquad (6)$$

We have calculated the relaxing specific volume of a rcp-liquid composite above and below the glass transition using the relaxation data obtained for polyvinylacetate (PVAc) [9–12]. For $v^l(T)$ and $v^{rcp}(T)$ we have anticipated the linear temperature dependencies given above. Fig. 2 gives the calculated specific volume curves for different experimental time constants. These results are in reasonable qualitative agreement with specific volume data [17]. In accordance with experimental observations for increasing cooling rates the $v(T)$-curves become increasingly bent and the operative transition anomaly expected at T_g is gradually shifted to higher temperatures with decreasing experimental time constants τ_{exp_T}. Moreover, with increasing cooling rates the true transition at T_{gs} becomes more and more hidden. The operative glass transition temperatures T_g shown in fig. 2 are unrelated to the true transition at T_{gs} but are a measure for the cross-over of the transition frequency ω_α with the experimental time scale τ_{exp_T}.

At high probe frequencies, the jump-like discontinuity of the static shear stiffness at T_{gs} transforms into a kink-anomaly (ii), which at even higher temperatures (transition from the slow motion to the fast motion regime) is followed by a mechanical slowing-down to zero. If a glass-forming liquid relaxes according to a Debye law, one calculates from (3) the real part of the complex dynamic shear modulus of a liquid [23] as

$$c^{'}_{44_{Debye}}(T, x_{rcp}(T), \tau_{exp_\omega}) = \frac{c^{\infty}_{44}(T, x^{rcp}(T))}{1 + (\omega_\alpha(T)\tau_{exp_\omega})^2} \qquad (7)$$

where $c^{\infty}_{44}(T, x^{rcp}(T))$ is the temperature-dependent shear stiffness as measured at very high frequencies which close to but still above TGT may significantly depend on the thermal treatment of the sample. By our definition, $c^{\infty}_{44}(T, x^{rcp}(T))$ depends on the concentration of the rcp's and on the temperature. In order to account for the effect of $x^{rcp}(T)$ on $c^{\infty}_{44}(T, x^{rcp}(T))$ we use the Voigt model [24] to account for the elastic interaction of the liquid part $c^l_{44}(T)$ and the rcp part $c^{rcp}_{44}(T)$ within the sample

$$c^{\infty}_{44}(T, x^{rcp}(T)) = c^l_{44}(T)(1 - x^{rcp}(T)) + c^{rcp}_{44}(T)x^{rcp}(T)$$

We assume for the elastic modulus of the liquid part $c^l_{44}(T) = c^{l_0}_{44}(1 + \alpha^l_{44}(T - T_{gs}))$ and for the rcp part $c^{rcp}_{44}(T) = c^{rcp_0}_{44}(1 + \alpha^{rcp}_{44}(T - T_{gs}))$ where $c^{l_0}_{44}, \alpha^l_{44}, c^{rcp_0}_{44}, \alpha^{rcp}_{44}, T_{gs}$ are constants. Since the mechanical properties of the rcp's are expected to deviate only slightly from those of the liquid phase, the measured data will be rather insensitive with respect to the chosen composite model (Voigt or Reuss) [24]. Finally we take into account the effect of the cooling/heating procedure on the elastic shear stiffness by combining eqs. (4,7). It turns out that the influence of the thermal history on the recovery of the elastic constants can be incorporated in the same formal way as it was done for the specific volume, yielding

$$c^{'}_{44}(T) = Q(T, \tau_{exp_T})c^{'}_{44_{Debye}}(T) \qquad (8)$$

According to the results shown in fig. 2, eq. (8) describes at least qualitatively the static and dynamic elastic behavior around the glass transition including thermal recovery effects. The genuine discontinuous change of the static shear modul at T_{gs} is well described. As mentioned above we have for the first time observed the discontinuous behaviour of the α-relaxation process for PVAc [9–12]. Therefore the $c^{'}_{44}(T)$-curves in fig. 2 have been calculated on the basis of data for the activation energy and the attempt frequency of the α-process of this material. Since PVAc has an almost vanishing scattering cross-section for shear phonons, the shear modulus is hard to measure. However the qualitative behaviour of the dynamic shear modulus shown in fig. 2 was often reported in literature (e.g. [25,26]). The cross-over of the hypersonic probe frequency with the internal glass relaxation process happens at temperatures well above T_{gs}. This indicates that the kink-like anomaly close to T_{gs} has *nothing* to do with a cross-over of the probe frequency with the α-relaxation time.

In conclusion, we have introduced a new working hypothesis treating the ideal glass transition as a dynamic phase transition. We identify the jump in the transition parameter $\omega_\alpha(T) = \tau^{-1}_\alpha(T)$ at $T = T_{gs}$, see eq. (1), as the fundamental feature of the glass transition. This

sole feature, when combined with standard knowledge on glasses, allows one to predict the temperature- and time- dependence of susceptibilities sensitive to the glass transition in good agreement with experimental data, reflecting at the same time phase transition and kinetic phenomena.

* supported by the *Deutsche Forschungsgemeinschaft*
** Laboratoire associé au CNRS UMR 7556

[1] C. A. Angell, K. L. Ngai, G. B. McKenna, P. F. McMillan, S. W. Martin, J. Appl. Phys. **88**, 3113 (2000)
[2] E. Donth, *Relaxation and Thermodynamics in Polymers, Glass Transition*, Akademie-Verlag, Berlin (1992)
[3] P. G. Debenedetti,*Metastable liquids: concepts and principles*, Princeton University Press (1996)
[4] S. R. Elliott, *Physics of amorphous materials 2nd ed.*, Longman Scientific&Technical (1990)
[5] I. Gutzow, J. Schmelzer, *The vitreous state*, Springer Berlin (1995)
[6] W. Götze, J. Phys. Cond. Matt. **11**, A1 (1999)
[7] K. Binder, J. Baschnagel, C. Bennemann, W. Paul, J. Phys. Cond. Mat. **11**, A47 (1999)
[8] P. G. Debenedetti, F. H. Stillinger, Nature **410**, 259 (2001)
[9] J. K. Krüger, K.-P. Bohn, R. Jiménez, Condensed Matter News **5**, 10 (1996)
[10] J. K. Krüger, K.-P. Bohn, R. Jiménez, J. Schreiber, Colloid Polym. Sci. **274**, 490 (1996)
[11] J. K. Krüger, P. Mesquida, J. Baller, Phys. Rev. **B60**, 10037 (1999)
[12] J.K. Krüger, R. Holtwick, A. le Coutre and J. Baller; Nanostructured Materials **12**, 519-522 (1999)
[13] J. Jäckle, Rep. Prog. Phys. **49**, 171 (1986)
[14] K. Binder, Berichte der Bunsengesellschaft für physikalische Chemie **100**, 1381 (1996)
[15] J. H. Gibbs, E. A. DiMarzio, J. Chem. Phys. **28**, 373 (1958)
[16] C. Meischner, B. Greiner, P. Hauptmann, E. Donth, Acta Polim. **37**, 453 (1986)
[17] A. J. Kovacs, J. Polym. Sci. **30**, 131 (1958)
[18] F. R. Schwarzl, F. Zahradnik, Rheol. Acta **19**, 137 (1980)
[19] G. Rehage, J. Macromol. Sci.-Phys. **B18**(3), 423 (1980)
[20] J. K. Krüger, K.-P. Bohn, M. Pietralla, J. Schreiber, J. Phys.: Cond. Matt. **8**, 10863 (1996)
[21] J. K. Krüger, K.-P. Bohn, J. Schreiber, Phys. Rev. **B54**, 15767 (1996)
[22] F. Lüty, J. Ortiz-Lopez, Phys. Rev. Lett. **50**, 1289 (1983)
[23] Herzfeld, Litovitz, *Absorption and dispersion of ultrasonic waves*, Academic Press New York (1959)
[24] T. R. Middya, A. N. Basu, in *Lattice Theory of Elastic Constants*, edited by S. Sengupta (Trans Tech Publications), Chapter 6 (1988)
[25] J. K. Krüger, L. Peetz, W. Wildner, M. Pietralla, Polymer **21**, 620(1980)
[26] J. K. Krüger, A. Marx, R. Roberts, H.-G. Unruh, M. B. Bitar, H. Nguyen-Trong, H. Seliger, Maromol. Chem. **185**, 1469 (1984)

FIG. 1. Activation Plot of $\omega_\alpha(T) = \tau_\alpha^{-1}(T)$ taken from refs. [9–12]. At temperatures below (a) no further relaxation could be found (see text).

FIG. 2. Specific volume v (curves a-c) and shear stiffness c_{44} (curves d-f) as a function of temperature calculated from eqs. (6,8) with different experimental time constants: (a) $\tau_{exp_T} = 10^9 s$ (b) $\tau_{exp_T} = 10^3 s$ (c) $\tau_{exp_T} = 10^{-1} s$ and (d) $\tau_{exp_T} = 10^8 s$, $\tau_{exp_\omega} = 10^8 s$ (e) $\tau_{exp_T} = 10^2 s$, $\tau_{exp_\omega} = 10^{-4} s$ (f) $\tau_{exp_T} = 10^{-1} s$, $\tau_{exp_\omega} = 10^{-6} s$. T_{g1}, T_{g2}: operative glass transition temperatures.

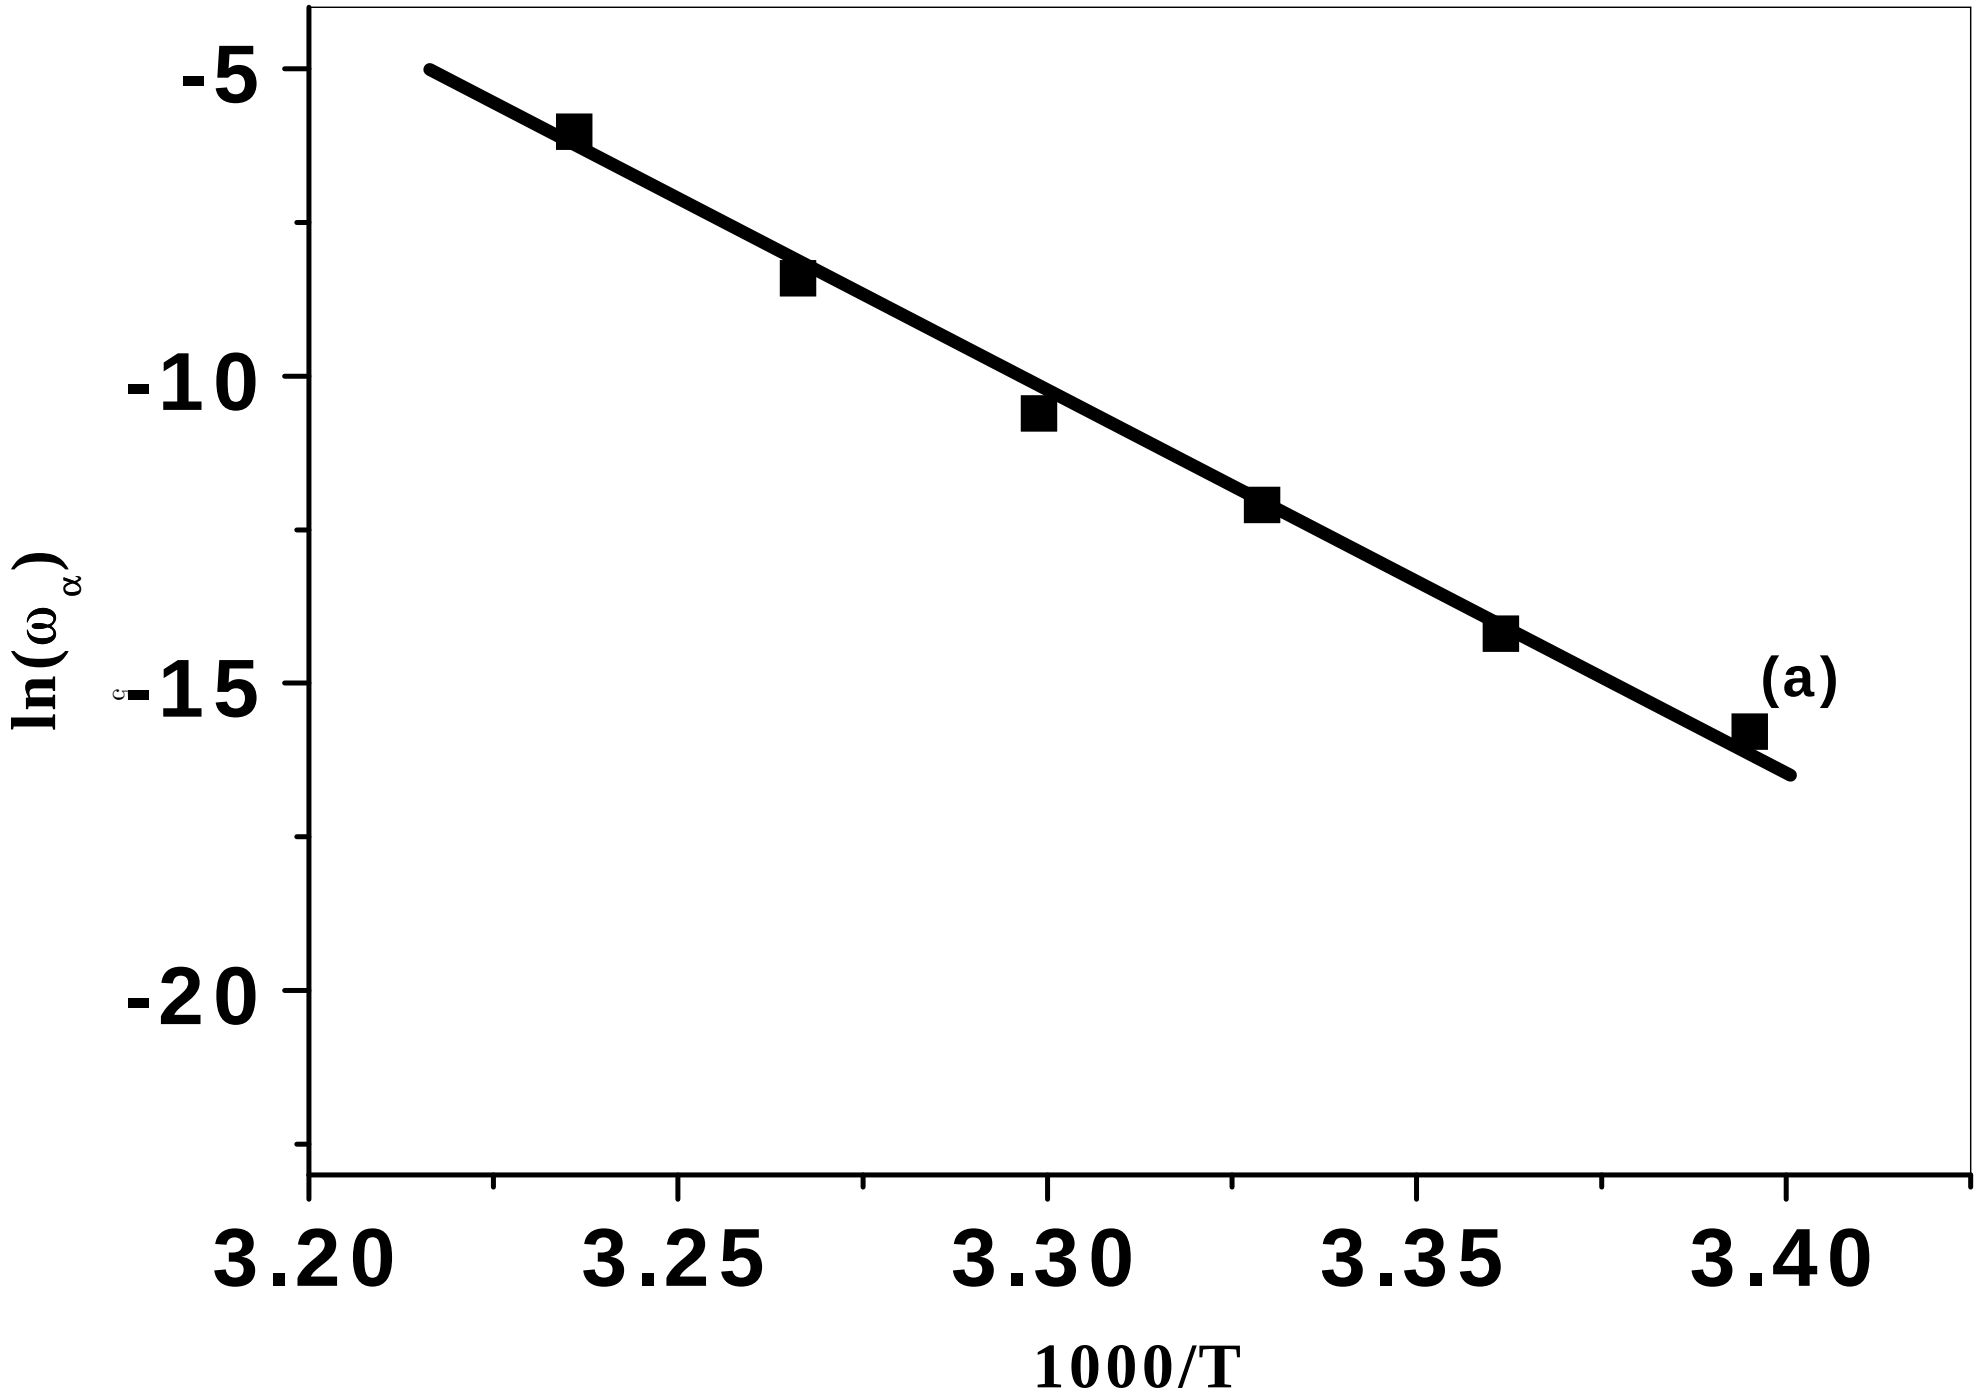
-5
-10
-15
-20
ln(ω_α)
3.20
3.25
3.30
3.35
3.40
1000/T
(a)

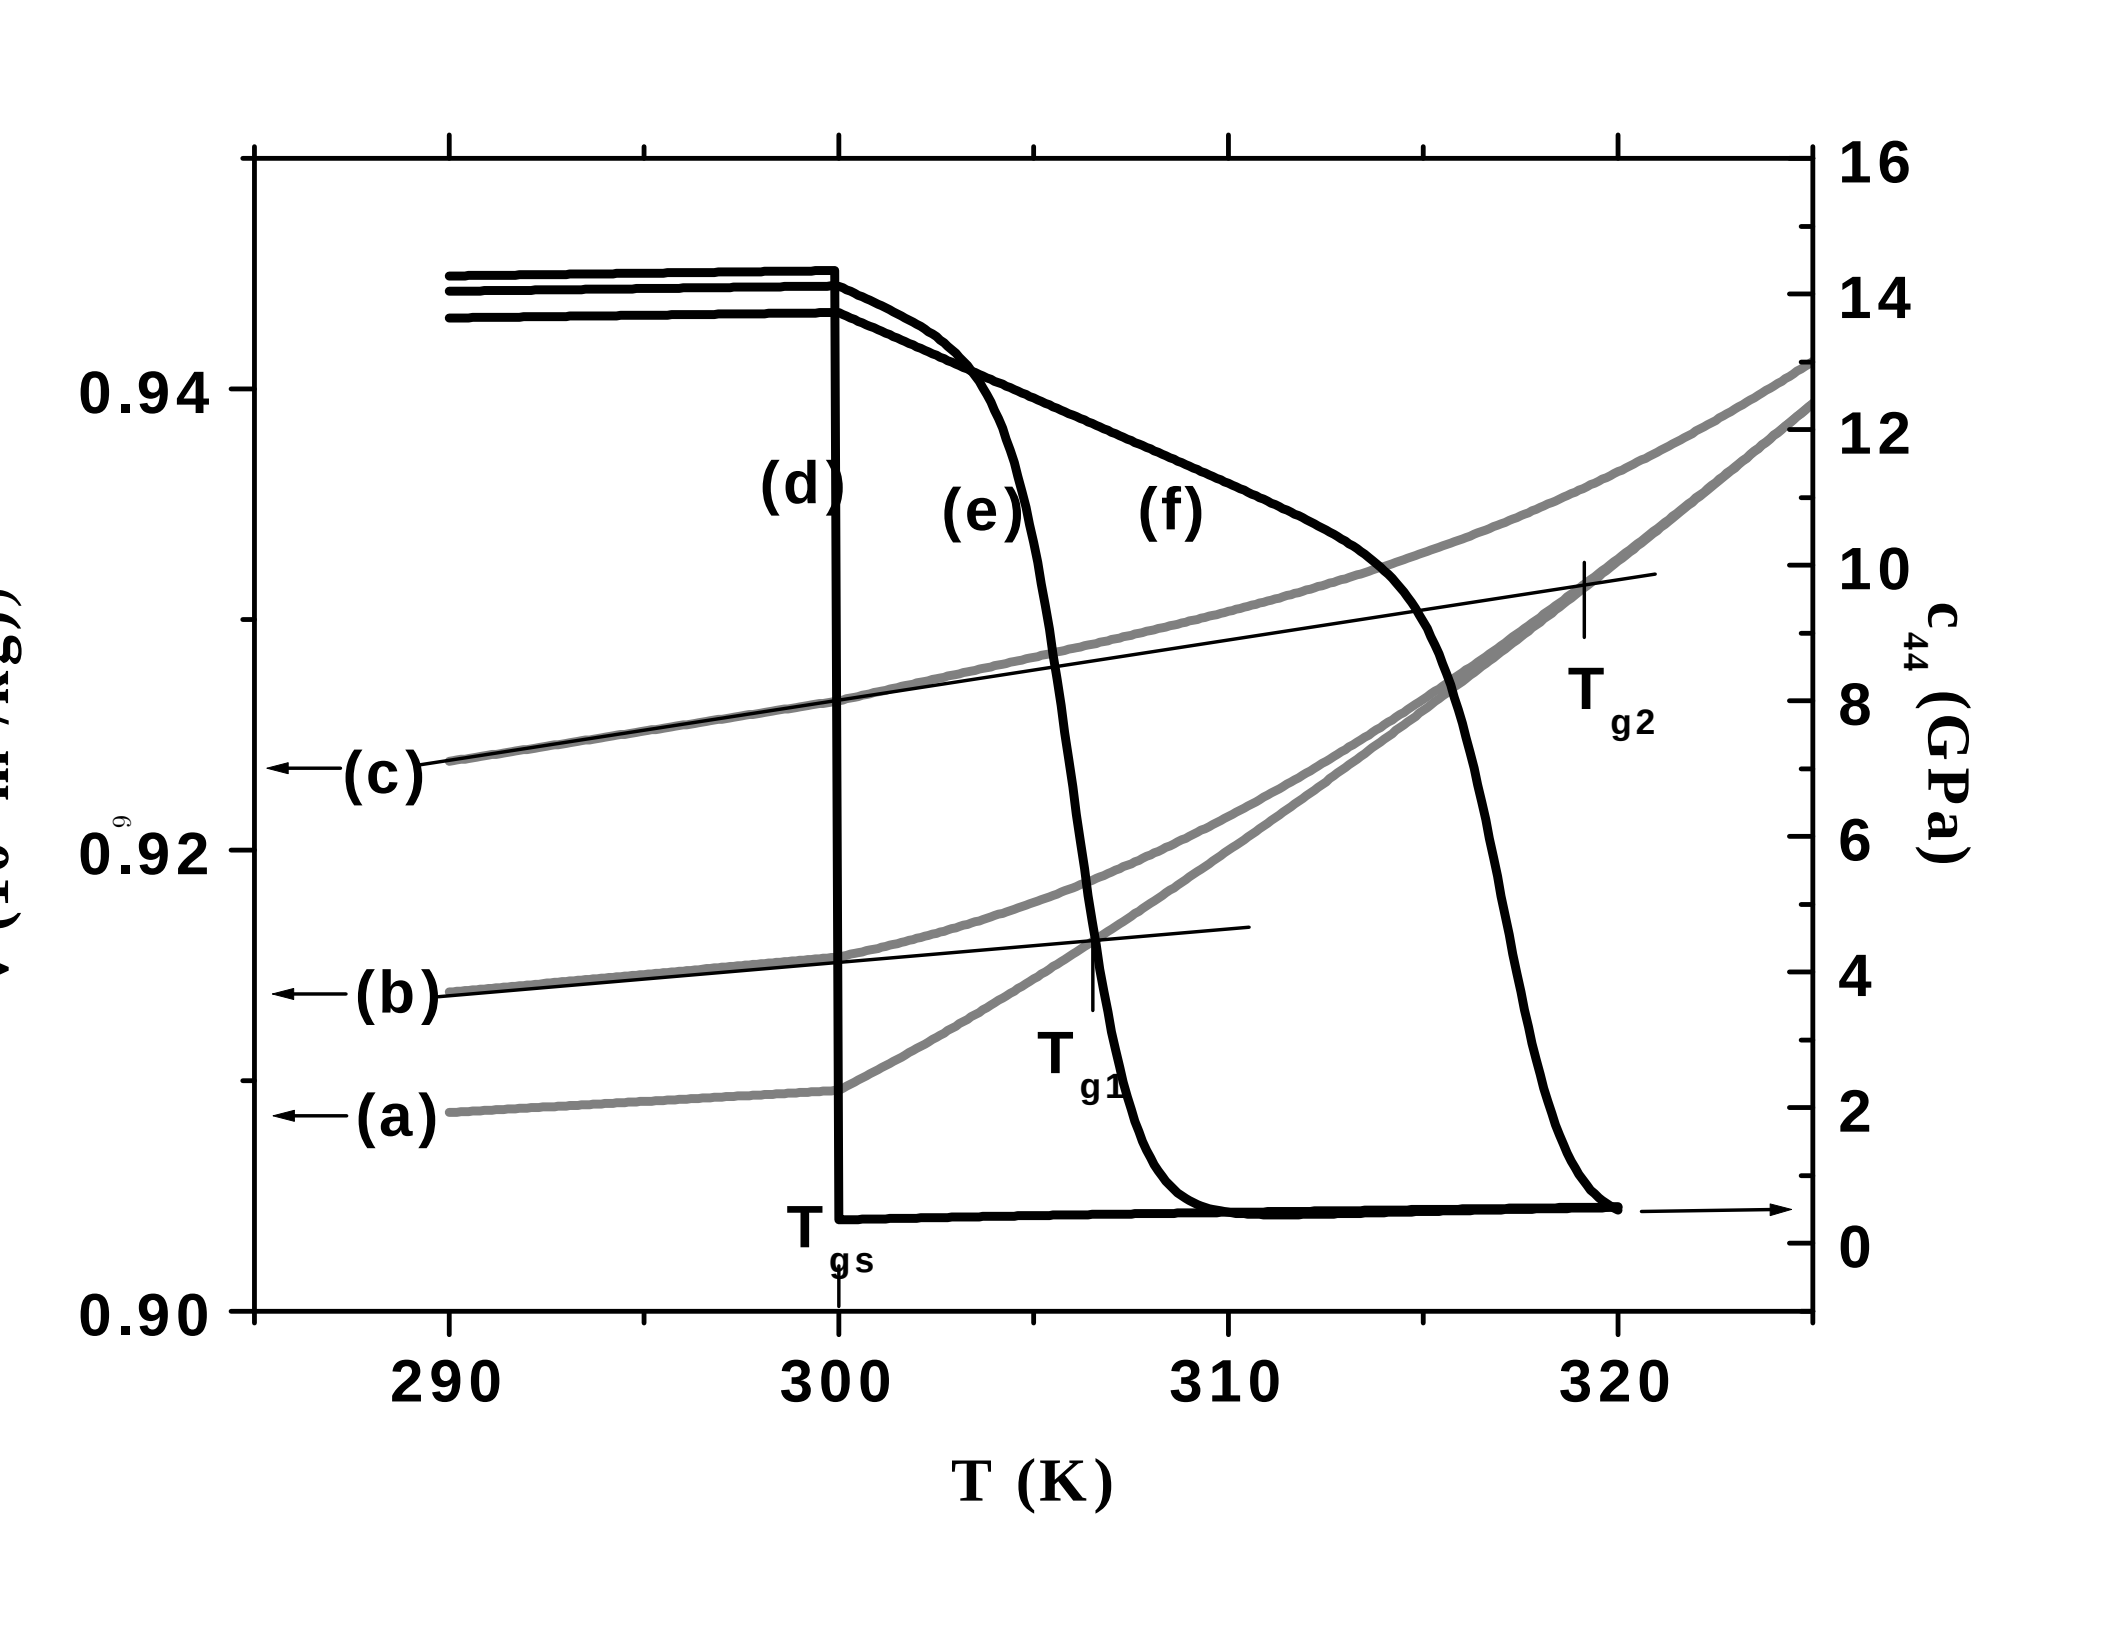
0.94
0.92
0.90
290
300
310
320
T (K)
16
14
12
10
8
6
4
2
0
C44 (GPa)
(a)
(b)
(c)
(d)
(e)
(f)
Tgs
Tg1
Tg2